

## Durham Research Online

---

### Deposited in DRO:

19 November 2021

### Version of attached file:

Accepted Version

### Peer-review status of attached file:

Peer-reviewed

### Citation for published item:

Danos, Andrew and Gudeika, Dalius and Kukhta, Nadzeya and Lygaitis, Ramunas and Colella, Marco and Higginbotham, Heather and Bismillah, Aisha N and McGonigal, Paul R and Grazulevicius, Juozas V and Monkman, Andrew P (2022) 'Not the Sum of their Parts: Understanding Multi-Donor Interactions in Symmetric and Asymmetric TADF Emitters.', *Journal of Materials Chemistry C*, 10 (12). pp. 4737-4747.

### Further information on publisher's website:

<https://doi.org/10.1039/D1TC04171A>

### Publisher's copyright statement:

his article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

---

## Use policy

The full-text may be used and/or reproduced, and given to third parties in any format or medium, without prior permission or charge, for personal research or study, educational, or not-for-profit purposes provided that:

- a full bibliographic reference is made to the original source
- a [link](#) is made to the metadata record in DRO
- the full-text is not changed in any way

The full-text must not be sold in any format or medium without the formal permission of the copyright holders.


Please consult the [full DRO policy](#) for further details.

# Journal of Materials Chemistry C

Materials for optical, magnetic and electronic devices

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: A. Danos, D. Gudeika, N. Kukhta, R. Lygaitis, M. Colella, H. Higginbotham, A. N. Bismillah, P. R. McGonigal, J. V. Grazulevicius and A. P. Monkman, *J. Mater. Chem. C*, 2021, DOI: 10.1039/D1TC04171A.

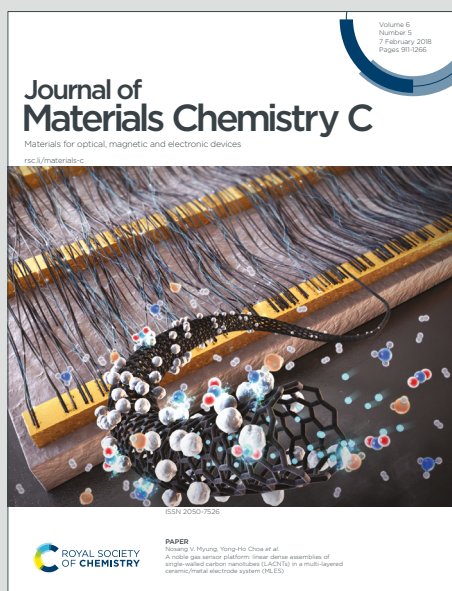

This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

# Not the Sum of their Parts: Understanding Multi-Donor Interactions in Symmetric and Asymmetric TADF Emitters

Andrew Danos<sup>1,†\*</sup>, Dalius Gudeika<sup>2,‡</sup>, Nadzeya A. Kukhta<sup>3,4,‡</sup>, Ramunas Lygaitis<sup>2</sup>, Marco Colella<sup>1</sup>, Heather F. Higginbotham<sup>1</sup>, Aisha N. Bismillah<sup>3</sup>, Paul R. McGonigal<sup>3</sup>, Juozas Vidas Grazulevicius<sup>2</sup> and Andrew P. Monkman<sup>1</sup>

<sup>1</sup>*Department of Physics, Durham University, South Road, Durham, DH1 3LE, UK*

<sup>2</sup>*Department of Polymer Chemistry and Technology, Kaunas University of Technology, Kaunas 51423, Lithuania*

<sup>3</sup>*Department of Chemistry, Durham University, South Road, Durham, DH1 3LE, UK*

<sup>4</sup>*Materials Science and Engineering Department, University of Washington, Seattle, Washington 98195, United States*

‡ These authors contributed equally

\* Email: andrew.danos@durham.ac.uk

## Abstract

A pair of thermally activated delayed fluorescence (TADF) emitters with symmetric and asymmetric D-A-D structure are investigated. Despite displaying near-identical photoluminescence spectrum and quantum yields, the symmetric material possesses significantly better delayed fluorescence characteristics and OLED performance. Building on a previous study of analogous D-A materials we are able to explain these differences in terms of different strengths of electronic interactions between the two donor units. This interaction lowers the energy of the TADF-active triplet state in the asymmetric molecule, increasing its singlet–triplet energy gap and leading to worse performance. This result therefore demonstrates a new strategy to selectively control the triplet states of TADF molecules, in contrast to established control of singlet states using host environment. These results also show that multi-donor TADF emitters cannot be understood simply as the sum of their isolated parts; these parts have different electronic interactions depending on their relative positions, even when there is no scope for steric interaction.

## Introduction

Due to tremendous research efforts in recent years, purely organic thermally activated delayed fluorescence (TADF) materials have proven their potential for optoelectronic applications.<sup>1</sup> Not only have TADF materials found utilization in highly efficient organic light emitting diodes (OLEDs),<sup>2–4</sup> but their emissive and triplet-management properties have also enabled cross-disciplinary applications in fluorescence sensing and imaging,<sup>5</sup> optical temperature sensing,<sup>6</sup> and catalysis.<sup>6</sup> The widely acknowledged success of TADF emitters is primarily due to their near optimal quantum efficiency in electroluminescent devices; 100% values can be achieved<sup>7</sup> in comparison to the 25% limit for conventional fluorescence emitters. Additional benefits include their largely reduced cost, lowered toxicity, and potential ability to achieve deep blue emission - each of which are intractable challenges for pre-existing rare- or heavy-metal containing organometallic phosphorescent emitters.<sup>8</sup> These merits have brought TADF emitters to the forefront of materials science, and intense research directed



towards deeper understanding of the underlying mechanism and development of novel compounds continues presently.

The TADF mechanism is based on a second-order spin-vibronic coupling between a charge transfer triplet state ( $^3\text{CT}$ ) and a local excited triplet ( $^3\text{LE}$ ) to mediate the up-conversion reverse intersystem crossing (rISC) of the coupled  $^3\text{LE}/^3\text{CT}$  triplet(s) to the emissive charge transfer singlet ( $^1\text{CT}$ ) state.<sup>9,10</sup> In turn, achieving fast rISC directly depends on the minimization of the singlet-triplet energy gap ( $\Delta E_{\text{ST}}$ ) – an essential, but not sufficient condition for the observation of TADF. Much work has been carried out to discover chemical motifs that minimize the  $\Delta E_{\text{ST}}$  gap, and correspondingly maximize rISC.<sup>11–16</sup> As a result of this multidisciplinary work, generic design rules for successful TADF emitters have emerged.<sup>17</sup> Primarily, bridging of sterically hindered electron donor (D) and acceptor (A) groups in a twisted D-A architecture commonly results in weakly overlapping highest occupied molecular orbital (HOMO) and lowest unoccupied molecular orbital (LUMO). Consequently, such materials frequently possess charge transfer (CT) states with low electron exchange energy.<sup>18–20</sup> In recent years through-space (exciplex-like) D-A interactions and non-overlapping single-molecule multi-resonant electronic structures have also been shown to deliver unexpected and outstanding TADF performance.<sup>21–26</sup>

The choice of specific D and A chromophores and any structural modulation of the dihedral angle between them is often the foremost tool for tuning of the CT character, emission energy, and reduction of  $\Delta E_{\text{ST}}$  towards engineering efficient rISC and TADF. However, additional undesirable effects such as red-shift and broadening of the emission as well as severe reduction of the oscillator strength<sup>27</sup> can also occur somewhat unpredictably. In attempts to realize narrow TADF emission of a target colour and high efficiency, several investigations into more subtle aspects of molecular design have been reported. Recently, binding the D and/or A chromophores through various linking topologies (*ortho*-, *meta*-, *para*-) was shown to be an effective strategy for fine-tuning the energy levels and couplings of the moieties.<sup>13,26,28–33</sup> For instance, in our previous work we have attributed the differences in the performance of isomeric TADF emitters to various resonance and inductive effects around the acceptor unit's aromatic  $\pi$ -system.<sup>29</sup> This work showed that control over the dihedral angle alone is insufficient for fast rISC and efficient TADF, and that chemically identical donors can induce different TADF properties purely based on the position in which they are installed. Despite different conjugation strengths at the *meta*- and *para*- positions (expected to lead to varying extents of molecular planarization) the dimethylacridine (DMAC) donor was also found to have the same dihedral angle at either position. This surprising result was explained in terms of the DMAC donor self-regulating its steric environment with the C-H bonds at the 1- and 8- positions. This final conclusion stands in contrast to other more compact donors such as carbazole,<sup>34,35</sup> with dihedral angles that are more susceptible to external influences. This property also makes DMAC an ideal donor for comparing more subtle aspects of molecular design, with the influence of dihedral angle variation largely controlled.

Another popular strategy in TADF material design involves introduction of additional donors, resulting in D-A-D or D-A-D' molecular architectures. A plethora of multicolour TADF emitters have been developed using this approach.<sup>36–44</sup> Even a number of white emitters with D-A-D' structure have been reported,<sup>45–47</sup> although it remains unclear how to correlate the properties of the D-A-D' materials from those of the individual D-A and D'-A analogues.<sup>48</sup> An early advance in the D-A-D approach was made by Adachi et al., who introduced multiple donors with mutual steric interactions. For instance, 4CzIPN is a high-performance green TADF emitter based on the multi-donor approach which has received sustained research attention.<sup>49–51</sup> While originally it was believed that introduction of multiple donors ensured fixed dihedral angles between the D and A, the cumulative electronic effect of the donors was more recently attributed to the sum of the donating fragments<sup>52</sup> in a 'bottom up' investigation. Similar recent reports into multi-carbazole systems have also attempted to explain findings in terms of influences of individual donor units<sup>53,54</sup> on the larger electronic system.



This multi-donor approach has also inspired a number of subsequent works.<sup>55–57</sup> For instance, Oh et al. focused on acceptor substitution pattern in a series of isomeric multi-donor TADF emitters, comprising carbazole and 2,4-diphenyl-1,3,5-triazine as the donor and acceptor, respectively.<sup>56,58</sup> Their thorough theoretical and experimental approach allowed them to unravel the complexity of the steric interactions between the donors. From the photophysical analysis, the authors concluded that 2-/3- and 2-/6-substitutions of the donors feature decreased energy gaps and shortened delayed fluorescence lifetimes by means of large dihedral angle of the donors. Such a dihedral effect allowed for a degree of control over the energy gap and a rISC rate, resulting in OLEDs with correlated efficiencies and roll-offs. While significant attention in this work was dedicated to the investigation of the steric effects (which dominate dihedral angles for carbazole donors<sup>34,35</sup>), many questions regarding the electronic communication in multi-donor TADF emitters remained unanswered.

Building on the previous findings of our group<sup>29,56</sup> and aiming to better understand the connection between analogous D-A and D-A-D molecules, we investigate two isomeric D-A-D TADF emitters comprised of a benzonitrile acceptor and acridine donors attached at the 2,5- or 2,6- positions of the acceptor. Comparison to previously reported D-A materials (facilitated by the self-regulating dihedral angle of DMAC<sup>59</sup>) allows us to compare these systems with minimal additional complexity introduced by the second D unit. Using a combination of experimental and theoretical methods, we demonstrate that electronic interaction between the donating moieties – modulated by the relative position of each – alters the <sup>3</sup>LE energy and thus also  $\Delta E_{\text{ST}}$  and TADF performance. We therefore demonstrate a viable strategy of selectively controlling the LE triplet energy in TADF multi-donor emitters, without altering the CT singlet energy. This provides a counterpart to the commonly-employed host tuning strategy that minimise  $\Delta E_{\text{ST}}$  by external action on the polarity-sensitive CT singlet state.<sup>3,60</sup> Furthermore, this work establishes that multi-donor TADF emitters cannot be understood simply as the sum of the donating fragments, or as perturbations of analogous D-A materials. Instead, emergent inter-donor interactions must be taken into account, which immediately disqualify such bottom-up approaches.


## Results

### Synthesis and characterisation

The two isomers (*o,m*)ACA (2,5-bis(9,9-dimethyl-9,10-dihydroacridin-10-yl)benzonitrile) and (*o,o*)ACA (2,6-bis(9,9-dimethyl-9,10-dihydroacridin-10-yl)benzonitrile) were synthesized by the procedures shown in **Scheme 1**, with full details in the SI. Earlier investigations of OLEDs using (*o,m*)ACA as a non-doped emitter have been previously reported.<sup>44</sup> The target compounds were prepared in yields of 58–61% through a Pd-catalyzed Buchwald-Hartwig cross-coupling reaction between 9,10-dihydro-9,9-dimethylacridine and 2,5-dichlorobenzonitrile or 2,6-dichlorobenzonitrile.

Additional thermal, electrochemical, and crystallographic properties of the two molecules are also included in the SI, demonstrating their near-identical physical properties – including equal electron affinity and ionisation potentials.



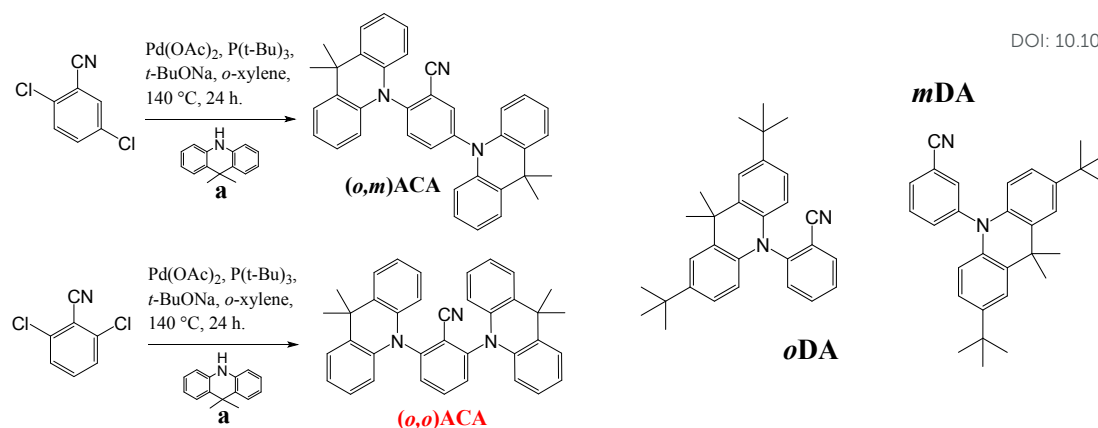

**Scheme 1.** Synthesis of *(o,m)*ACA and *(o,o)*ACA (left), and structures of previously investigated D-A materials<sup>29</sup> (right).

### Photophysical properties

In anticipation of their applications in OLEDs and guided by optimised doping concentrations reported for similar DMAC containing TADF materials,<sup>13,61</sup> the optical properties of *(o,m)*ACA and *(o,o)*ACA were investigated primarily in 25% v/v co-doped evaporated films using bis[2-(diphenylphosphino)phenyl]ether oxide (DPEPO) as host. **Figure 1a** shows the UV-vis absorption, photoluminescence (PL), and time-resolved low temperature phosphorescence spectra (PH) of the films. Also shown are comparisons of the PL (**Figure 1b**) and PH spectra (**Figure 1c**) with those of *o*DA and *m*DA (10% w/w drop cast films in DPEPO), the single D and A analogues.

The similarities in optical properties between *(o,m)*ACA and *(o,o)*ACA are striking, with UV-vis and PL spectra nearly identical (**Figure 1a**). This trend is also preserved in a range of different solvents (**Figures S9 and S10**). *o*DA and *m*DA also have very similar singlet energies to each other in DPEPO (taken from PL onset wavelength), although with *m*DA marginally higher in energy than *o*DA and with broader PL band. This trend is consistent with what was previously reported for these D-A materials in polymer host zeonex, and arises from differences in electron-hole separation in the CT excited state<sup>62</sup> as well as differences in acceptor strength at different locations around the central benzonitrile ring.<sup>29</sup> Key photophysical properties are presented in **Table 1**, with the similarities in singlet energy and PLQY strongly indicating that both *(o,m)*ACA and *(o,o)*ACA emit through the same CT state, formed by the donor unit *ortho*- to the acceptor unit. Conversely, the *meta*- donor unit in *(o,m)*ACA is expected to form a higher-energy CT state (as it does in *m*DA compared to *o*DA), and thus must have limited influence on the singlet state properties in *(o,m)*ACA – evidenced by its identical PL spectrum to *(o,o)*ACA, which does not possess this structural feature.


Both *(o,m)*ACA and *(o,o)*ACA have significantly lower singlet state energies than the D-A materials, despite both lacking the *t*Bu donor substituents that make it more strongly electron donating.<sup>61</sup> We note that due to this structural difference the energies of the D-A and D-A-D materials should not be compared directly – only the trends within each pair. Although the absence of the *t*Bu groups would typically lead to weaker CT strength and blue-shifted emission, the opposite observation here hints at cooperative effects between the two donors yielding a stronger overall CT state than each D can generate alone. Similar effects are likely responsible for the different emission colours of 4CzIPN/2CzIPN, 4CzPN/2CzPN (both pairs green/blue<sup>49,52</sup> with additional/fewer Cz units) and other multi-carbazole systems.<sup>56</sup> However, this comparison is complicated by the potential for steric interactions between neighbouring carbazoles.<sup>34</sup> Such steric interactions can be disregarded for the






well-spaced DMAC donors in the present materials though, giving clearer insight into the purely electronic effects associated with different substituent positions.

In terms of triplet energies the materials show more noticeable differences. The triplet energy of ***m*DA** (2.95 eV, from PH onset wavelength) is higher than that of ***o*DA** (2.91 eV), which was previously explained in terms of different D-A coupling strengths and conjugation at different positions relative to the A, arising from the effects of electronic resonance structures. The triplet energy of ***(o,m)*ACA** (2.81 eV) is surprisingly significantly lower than that of ***(o,o)*ACA** (2.86 eV). In both materials the common ***o*DA** sub-unit appears to control the lowest energy triplet state, but it is not readily apparent why ***(o,m)*ACA** has a significantly lower triplet energy (50 meV) than ***(o,o)*ACA**. Indeed, the only structural difference is the presence of the ***m*DA** sub-unit in ***(o,m)*ACA**, which has a higher intrinsic triplet energy. Combined with near-identical singlet energies, this lower triplet energy therefore also leads ***(o,m)*ACA** to have a significantly larger  $\Delta E_{ST}$  gap. Although it is not immediately clear how this intrinsically higher triplet energy structural subunit could lead ***(o,m)*ACA** to have a lower overall triplet energy, the consequences of this difference are immediately evident in subsequent measurements.

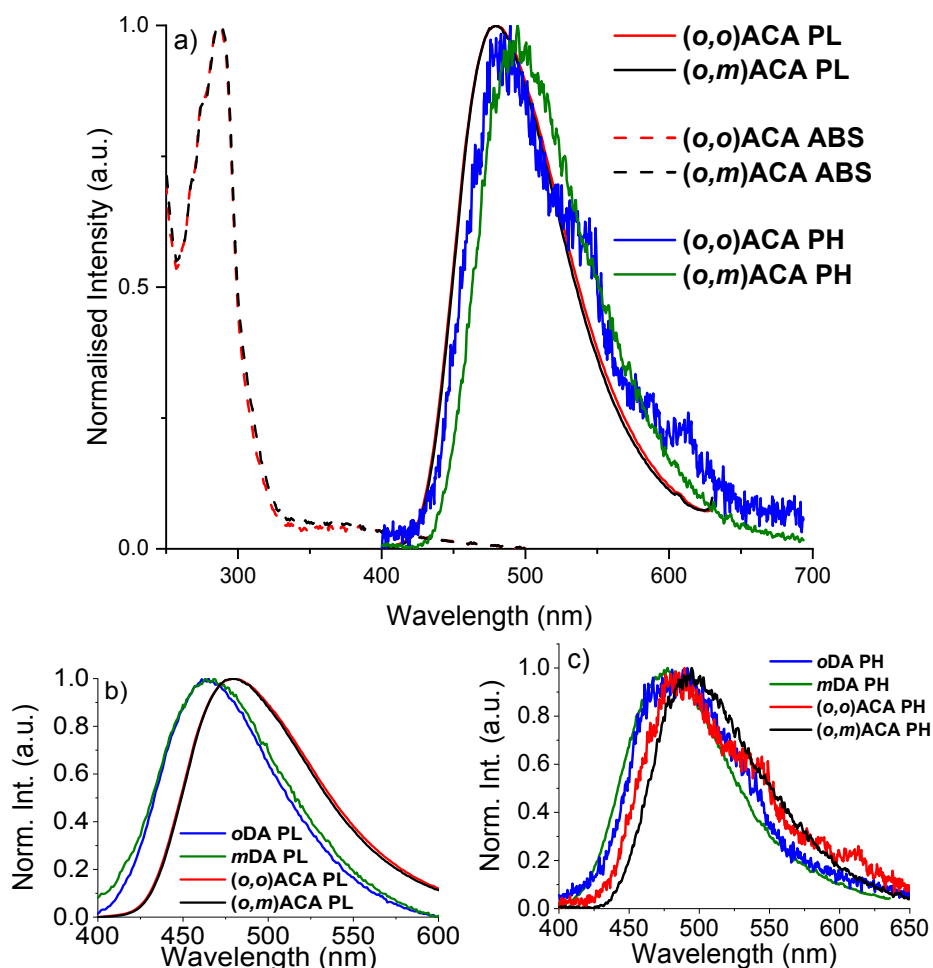

**Figure 1:** a) Absorption (ABS), photoluminescence (PL) and phosphorescence (PH) spectra of ***(o,m)*ACA** and ***(o,o)*ACA** in DPEPO films, b) Comparison of PL spectra with previously investigated D-A materials (also in DPEPO host), and c) comparison of PH spectra of the same. PH spectra recorded at >50 ms delay following pulsed 355nm excitation, with sample at 80 K.



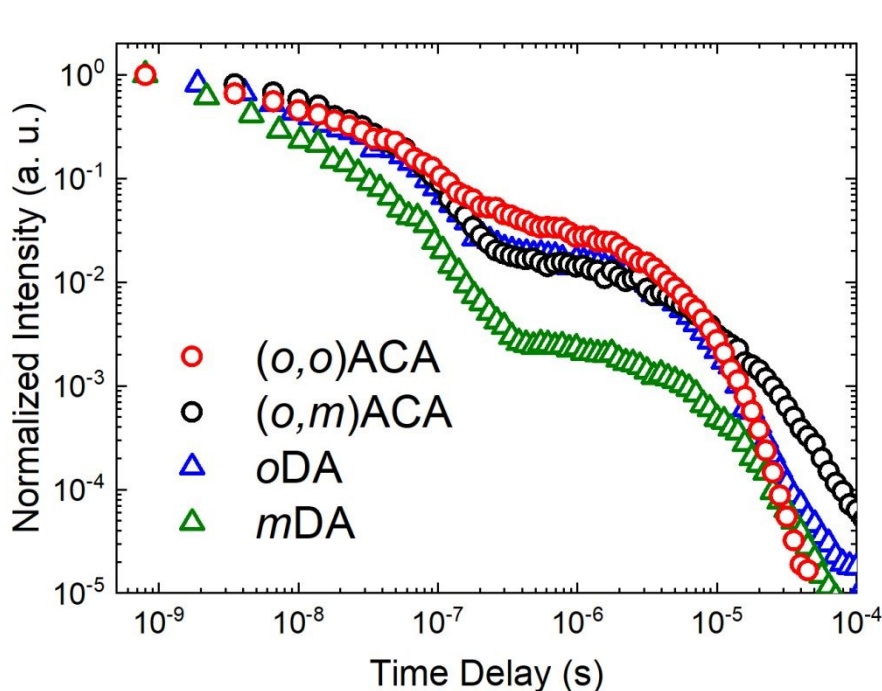

View Article Online  
DOI: 10.1039/D1TC04171A

**Figure 2:** Emission decay kinetics of D-A-D and D-A materials at room temperature in DPEPO films.

The emission decay kinetics of *(o,m)*ACA and *(o,o)*ACA are presented in **Figure 2**, alongside those of *mDA* and *oDA*. Similar to what was previously observed with the D-A materials, the individual time-resolved spectra that make up the *(o,o)*ACA and *(o,m)*ACA decays (**Figures S6** and **S7**) stayed roughly constant throughout the prompt fluorescence time regime (PF, 1-100 ns), later undergoing a slight spectral redshift through the delayed fluorescence (DF, 100 ns onward). This behaviour is typical of TADF materials with C-N linkages, arising from structural relaxation and/or dispersion of rISC rates associated with a distribution of molecular geometries and CT energies.

Overall the decay kinetics of *(o,o)*ACA and *(o,m)*ACA are much more alike than those of *mDA* and *oDA*. In particular the similar PF decay lifetimes (**Table 1**) strongly suggest that the emission emerges from the same CT state in both materials (i.e. that formed between the acceptor and an *ortho*-donor). In contrast the PF lifetimes are considerably different in *mDA* and *oDA*, reflecting the different CT states which give rise to these emission regimes in those two materials.

In the DF regime the delayed emission is significantly stronger and more rapid for *oDA* than for *mDA*, previously explained due to the different donor-acceptor electronic couplings at the different positions around the benzonitrile ring. While the DF emission is both weaker and slower in *(o,m)*ACA than in *(o,o)*ACA, the differences between the D-A-D materials are much less pronounced than for the D-A materials. Nonetheless, this inferior DF performance in *(o,o)*ACA presumably results from smaller relative rates of ISC (controlling DF intensity) and smaller rates of rISC (controlling DF decay rate) extracted by kinetic fitting of the decays.<sup>63</sup> In *(o,m)*ACA and *(o,o)*ACA the established differences in  $\Delta E_{ST}$  are able to explain these differences, as both processes rely on near-isoenergetic electronic states to make the otherwise spin-forbidden process rISC proceed at appreciable rates.






**Table 1:** Photophysical properties of emitters in DPEPO filmsView Article Online  
DOI: 10.1039/D1TC04171A

	$S_1$ (eV) <sup>a</sup>	$T_1$ (eV) <sup>b</sup>	$\Delta E_{ST}$ (meV) <sup>c</sup>	PLQY <sup>d</sup>	PF lifetime (ns) <sup>e</sup>	DF lifetime ( $\mu$ s) <sup>e</sup>	$k_f$ ( $\times 10^6$ s <sup>-1</sup> ) <sup>f</sup>	$k_{ISC}$ ( $\times 10^7$ s <sup>-1</sup> ) <sup>f</sup>	$k_{rISC}$ ( $\times 10^6$ s <sup>-1</sup> ) <sup>f</sup>
( <i>o,m</i> )ACA	2.89	2.81	80	70	62 $\pm$ 12	17	3.6	1.5	0.6
( <i>o,o</i> )ACA	2.88	2.86	20	75	80 $\pm$ 20	8.7	4.3	2.7	1.8

<sup>a</sup> from steady-state PL onset<sup>b</sup> from PH onset (>50ms delay, 80K)<sup>c</sup>  $S_1-T_1$ <sup>d</sup> measured in integrating sphere under nitrogen, 310nm excitation<sup>e</sup> from exponential fitting of PF or DF decay regions<sup>f</sup> Rates of fluorescence ( $k_f$ ), ISC ( $k_{ISC}$ ), and rISC ( $k_{rISC}$ ) from kinetic fitting of PF and DF region<sup>63</sup>

## OLED performance

The electroluminescence performances of (*o,o*)ACA and (*o,m*)ACA were investigated in a previously optimised<sup>13,61,64–66</sup> device architecture consisting of ITO | NPB (40 nm) | TSBPA (10 nm) | emitter:DPEPO x vol% (30 nm) | DPEPO (10 nm) | TPBi (40 nm) | LiF (1 nm) | Al (100 nm). The concentration of emitter in the emissive layer was optimised at 20% for (*o,o*)ACA, with this concentration then also used for (*o,m*)ACA. The key electroluminescence properties of the devices are presented in **Figure 3**, and in **Table 2**. This device architecture relies on DPEPO for electron transport through the emissive layer, with the DMAC-containing emitter providing hole transport. Consequently, (*o,o*)ACA devices using hole-transporting mCP as the emissive layer host (with no material capable of providing electron transport) displayed slightly blue-shifted emission spectra but much lower efficiencies (typically <10% EQE<sub>max</sub>, **Figure S8**). This is despite the triplet energies of the mCP (~2.97 eV)<sup>67</sup> and (*o,o*)ACA (2.86 eV) appearing compatible from photophysical measurements.

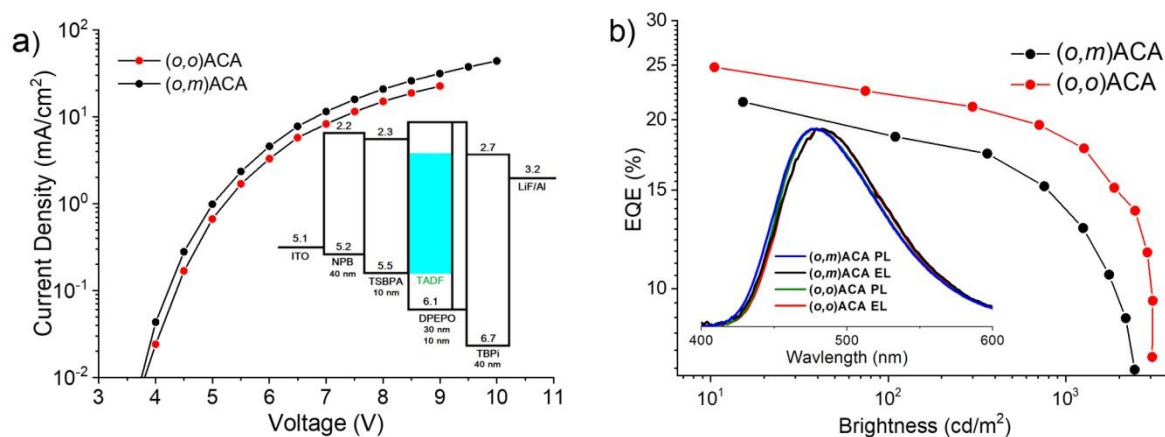**Figure 3:** OLED performance of D-A-D materials: a) I-V curves with device stack inset. b) EQE curves with EL spectra inset.

**Table 2:** OLED performance of D-A-D materials

	Turn on Voltage (V)	EQE <sub>max</sub> (% @ cd/m <sup>2</sup> )	EQE <sub>100</sub> (% @ cd/m <sup>2</sup> )	EQE <sub>1000</sub> (% @ cd/m <sup>2</sup> )	EQE <sub>Max Brt</sub> (% @ cd/m <sup>2</sup> )	CIE (x,y)
<b>(o,m)ACA</b>	4.0	21.4 @ 15	18.6 @ 109	12.8 @ 1250	5.6 @ 2511	0.18,0.33
<b>(o,o)ACA</b>	4.0	24.8 @ 10	22.5 @ 74	17.8 @ 1266	9.5 @ 3090	0.18,0.33

The near-identical electroluminescence colour (and CIE coordinates) of the **(o,o)ACA** and **(o,m)ACA** devices are in line with their near-identical film PL spectra. The near identical I-V curves also indicate near identical charge transport properties as well. We note that the emission colour is not as deep-blue as similar materials reported by Noda et.al,<sup>68</sup> confirming that the analogous diphenylacridine D unit is a weaker electron donor than DMAC. The maximum external quantum efficiencies (EQE<sub>max</sub>) of the two emitters are both in line with their similar PLQYs and different rISC rates, which govern OLED performance in the low-driving regime where rISC competes favourably with other quenching mechanism.

At higher driving voltages the performance of the **(o,m)ACA** device suffers considerably, as the same quenching processes that rISC competes with at low driving conditions scale strongly with current and exciton density. Normalised EQE curves are presented in **Figure S8** to facilitate comparison of this efficiency roll-off behaviour. Accordingly, the maximum brightness that the **(o,m)ACA** device can achieve is also lower. All of this behaviour is consistent with its lower rate of rISC, leaving it unable to harvest triplet states fast enough to avoid multi-exciton or charge-exciton quenching and degradation processes at larger driving currents. While the **(o,o)ACA** device also suffers quenching at higher driving, it is able to resist these processes more effectively due to its faster rISC rate.

The device performance is therefore entirely in line with expectations built upon the preceding optical results. We note that alongside the following physical insights arising from comparison of **(o,m)ACA** and **(o,o)ACA**, these results also establish both materials as objectively high-performance cyan TADF emitters. Such emitters with good TADF but less-than-ideal emission colour are currently enjoying expanded utility as sensitizers for deep-blue hyperfluorescence OLEDs.<sup>53,65,69–73</sup>

## Discussion and DFT calculations


As previously stated, all of the optoelectronic results in the previous section flow logically from the observation of similar singlet but different triplet energies for **(o,m)ACA** and **(o,o)ACA**. From a materials design perspective, the interesting question is *why* the triplet energies are so different, despite their similar chemical subunits and identical singlet energies. This question is especially difficult to answer as it goes against the trend established in the simpler **oDA** and **mDA** materials. This outcome means that the underlying cause must somehow be an emergent property arising from the presence of both donors and their resulting interactions – interactions absent in the D-A materials. If this were not the case, (i.e. if these materials behaved simply as the sum of their D-A analogues/fragments) we would expect the triplet energies to either be identical, or to follow the same trend as seen for the D-A materials with the **mDA** fragment leading to higher overall triplet energy in **(o,m)ACA** – in conflict with observation.



To better understand this behaviour we turn to DFT calculations. Calculations were performed with the Gaussian 09 package<sup>74</sup> using isolated molecules optimized at the rBMK/6-31G(d) level in gas phase. The spectroscopic properties of the molecules and their excited states were calculated by means of time-dependent DFT (TD-DFT)<sup>75</sup> also employing the 6-31G(d) basis set. The BMK functional was chosen as it has shown to be adequately reliable for the description of the low energy excited states in D–A CT compounds (including *o*DA and *m*DA), both by us<sup>29,61,76–78</sup> and by others including in benchmarking studies.<sup>79–81</sup>

**Figure 4** shows the NTOs and energies calculated for relevant triplet and singlet states in (*o,m*)ACA and (*o,o*)ACA. By inspecting the singlet NTOs in (*o,m*)ACA we first note that the CT singlet associated with the *ortho*- donor ( $S_1$ ) is lower in energy than that associated with the *meta*- donor CT state ( $S_2$ ). This is in agreement with expectations and the trends established for *o*DA and *m*DA, while the similarities between the donor/acceptor-centred NTOs here and donor/acceptor-centred HOMO/LUMO distributions previously reported for *o*DA and *m*DA confirm that these are predominantly CT transitions. In (*o,o*)ACA the  $S_1$  and  $S_2$  states are much closer in energy, and each involves both of the *ortho*- donor units. We suggest that these represent symmetric ( $S_1$ ) and antisymmetric ( $S_2$ ) combinations of otherwise degenerate CT states associated with either the left or right donor individually, and that the involvement of both donor units may contribute to the slightly faster  $k_f$  and higher PLQY observed for (*o,o*)ACA. This is analogous to the formation of symmetric (bonding) and antisymmetric (antibonding) molecular orbitals from combinations of degenerate atomic orbitals (**Figure 5a**). For the first two triplet states of CT nature similar trends are observed.



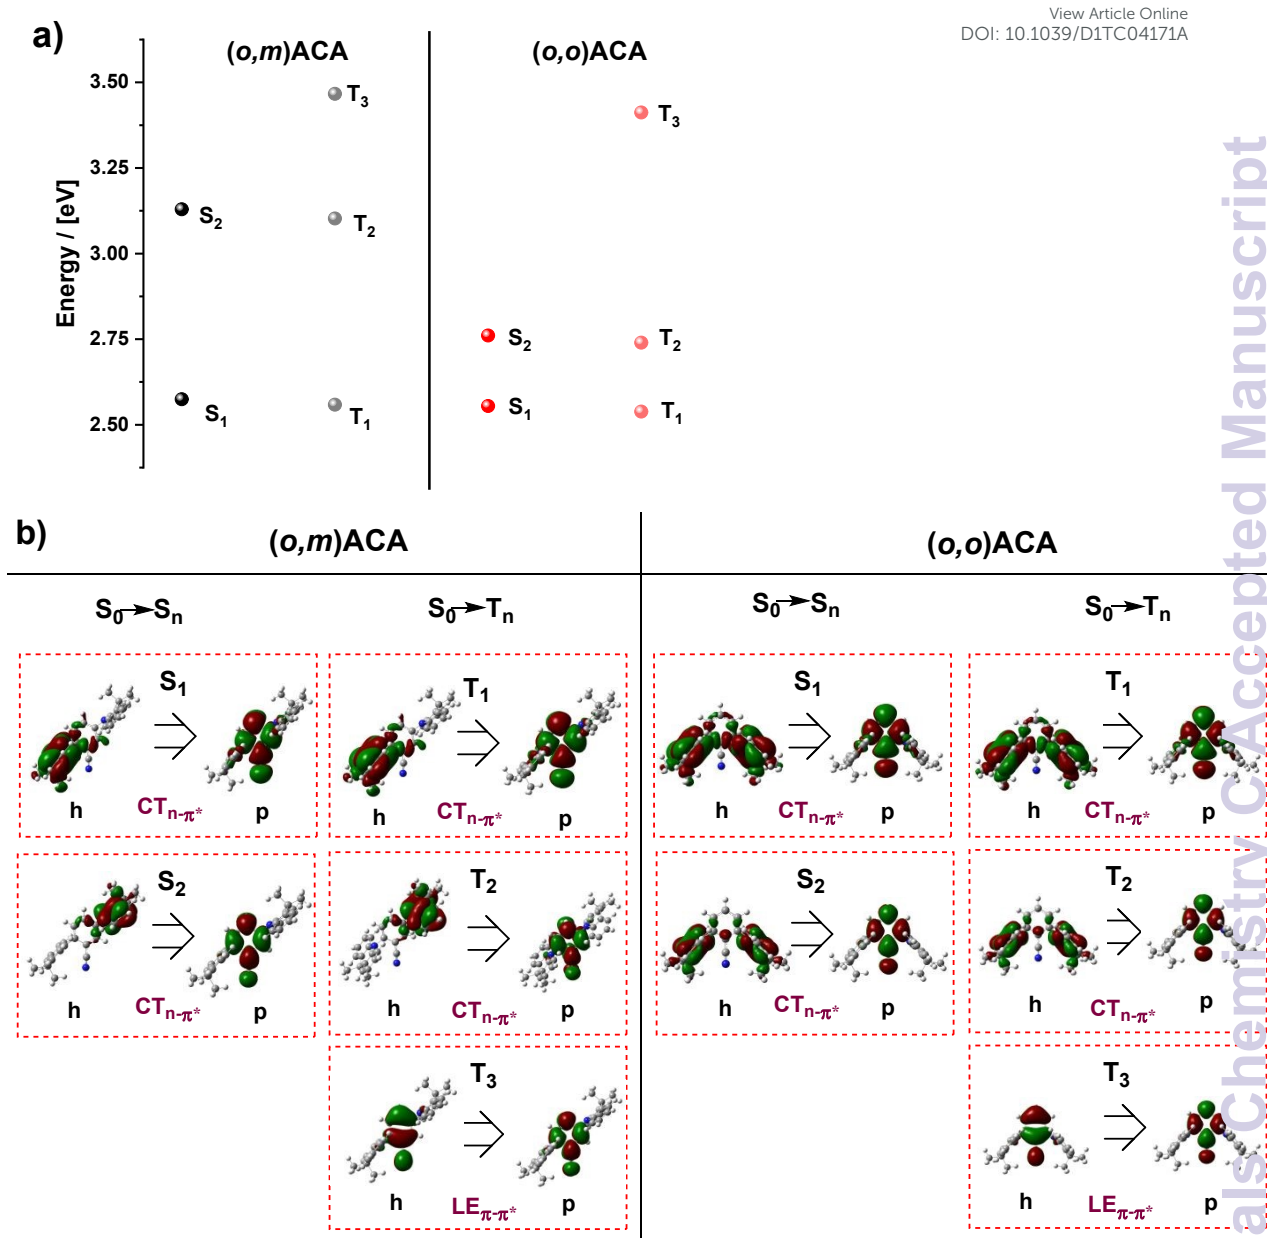

**Figure 4:** a) Adiabatic singlet / triplet energy diagram of (o,m)ACA and (o,o)ACA (TDA-DFT rBMK/6-31G(d)); b) selected set of natural transition orbitals (NTO) of (o,m)ACA and (o,o)ACA (TDA-DFT rBMK/6-31G(d)) (isovalue = 0.01)).

The first triplet state of LE nature is  $T_3$ , centred on the A unit in both materials and with nearly identical NTOs. This LE triplet state is the one relevant to vibronic coupling and rISC, and corresponds to the same triplet state identified by phosphorescence measurements in the previous sections (labelled in that section as  $T_1$ , with CT triplet states frequently non-emissive). To discount the alternative assignment (i.e, PH from CT states), we note that although the PH spectra are not structured, this alone is not enough to assign CT character to the PH state. Ultimately in the discussions below we present a mechanism that can cause the LE triplet states to be significantly different in energy while leaving CT singlet states unaffected – as is observed experimentally. In contrast, we are not aware of any mechanism that could explain different CT triplet states in (o,m)ACA and (o,o)ACA while leaving CT singlet states unaffected.

Interestingly, the calculated  $T_3$  energies of **(o,m)ACA** and **(o,o)ACA** are in the opposite order as found experimentally, with about the same difference in triplet energies in both cases ( $\sim 50$  meV). In the following discussion we propose a mechanism that explains the observed triplet energy ordering and why this is not reflected in calculations. We note that the reason for the experimental **(o,m)ACA** triplet energy being lower than **(o,o)ACA** cannot be due to the combination of individual couplings of the A to the two D units. If this were the case we would expect the two materials to either have identical triplet energies (from coupling between the A and the *ortho*-D in each material), or for **(o,m)ACA** to have a higher triplet energy than **(o,o)ACA** (due to coupling between A and *meta*-D, which is intrinsically higher in energy as in **mDA**). Any such state-mixing between LE and CT states is also unlikely to be a contributing factor, due to the forbidden nature of mixing these states with different orbital symmetries.<sup>82,83</sup>

Instead we propose that the LE  $T_3$  states in both **(o,m)ACA** and **(o,o)ACA** interact with higher-lying LE states delocalised across both donor units (D-D states). A representative state diagram is presented in **Figure 5b**, showing how these unoccupied electronic states would form. A similar explanation was recently employed to explain the performances of a series of differently connected multicarbazole TADF materials, although that study invoked the active participation of delocalised multi-D or multi-A states in the formation of CT states. The conclusions of that work are also complicated by the potential for additional steric interactions between the carbazole donors.<sup>53</sup> These factors are avoided here by the use of well-spaced donors, and the ability of DMAC to manage its own steric environment.<sup>29</sup>


The proposed D-D states are (to first approximation) formed by linear combinations of the individual donor LE states (**Figure 5b**), and so one of these D-D states (the symmetric combination) is expected to be the lowest-energy LE singlet state in each molecular system. This expectation is supported by the absorption spectra of the two materials, discussed in more detail below and presented in **Figure S9**, which show the first major absorption band at a wavelength consistent with DMAC.<sup>84</sup> These D-D states (in either singlet or triplet multiplicity) are therefore also some of the closest LE states in energy to the **(o,m)ACA** and **(o,o)ACA** LE  $T_3$  state, and so are likely candidates for explaining why their energies differ. These D-D states are also unoccupied, which explains why the DFT calculations are unable to accurately predict the order of **(o,m)ACA** and **(o,o)ACA**  $T_3$  energies compared to experiment. Accurately accounting for such interactions with unoccupied states would instead require more advanced multireference or complete active space *ab-initio* methods, which are impractical for molecules of this size.

Applying molecular orbital theory in the symmetric and asymmetric D-A-D systems, we can infer several properties of the D-D states and how they would differ. Due to different conjugation strengths across the linker unit for **(o,m)ACA** (**pD-D** state) than for **(o,o)ACA** (**mD-D** state), we would expect the **pD-D** state to be lower in energy and have larger electron density on the central bridge region (**Figure 5b**). This would subsequently lead to a larger orbital overlap between the **pD-D** state and the  $^3\text{LE}_A$  state associated with the A unit ( $^3\text{LE}_A$ ) in **(o,m)ACA** as compared to **mD-D** in **(o,o)ACA**. The resulting state mixing between D-D and  $^3\text{LE}_A$  states lowers the observed phosphorescence energies in both materials compared to calculations, which cannot account for interactions with unoccupied orbitals. Due to increased orbital overlap the state mixing with the  $^3\text{LE}_A$  is more extensive for **pD-D** than for **mD-D**, leading to a yet lower triplet energy in **(o,m)ACA** and the observed ordering of experimental phosphorescence energies (**Figure 5c**). While other higher-energy LE states would also be influenced by interactions with the D-D states, none of these higher LE states are measured or expected to influence the TADF properties. Due to differences in the shapes of their excited state wavefunctions leading to zero overlap integral, the CT states are not expected to interact with the D-D states, and so are totally unaffected both in calculations and experiment (identical PL spectra and  $S_1$  energies).





Supporting these expected properties of the D-D states, similar trends in excited state energy in other *para*- or *meta*- linked bichromophores are commonly reported,<sup>67,85,86</sup> for example the higher triplet energy of mCBP (2.8 eV) compared to *para*-linked CBP (2.6 eV). Donor interactions of a similar nature over *para*- linkages may also be responsible for lower energy emission in recently reported multi-resonance materials using *para*- bichromophore designs,<sup>26</sup> or when decorated with additional carbazoles.<sup>33</sup> This explanation is also entirely consistent with the effects of donor position on excited-state energies previously reported for *oDA* and *mDA*<sup>29</sup> and by others in analogous systems.<sup>32</sup>

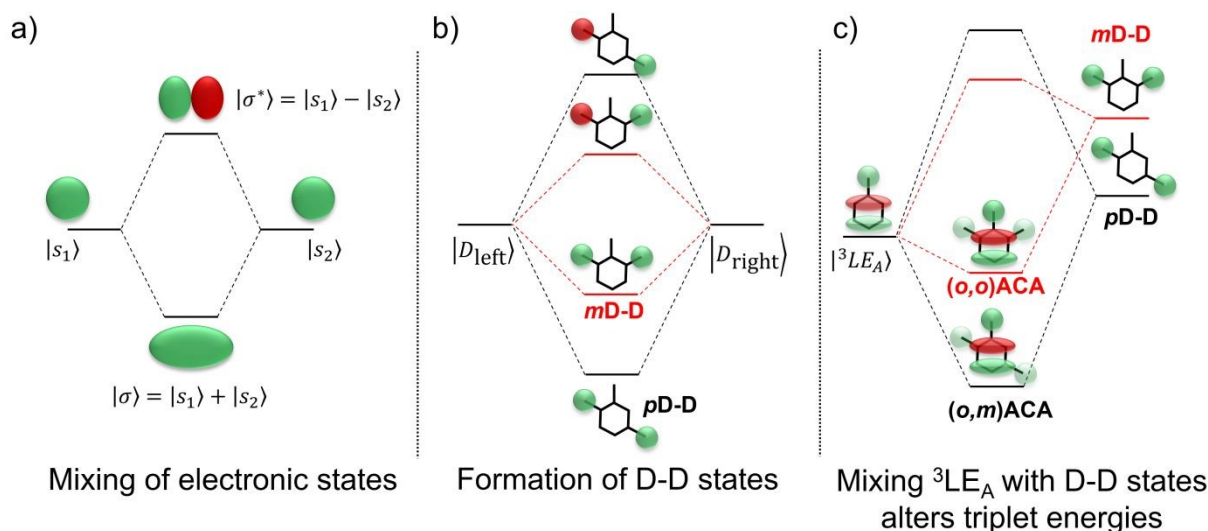

**Figure 5:** State diagrams showing: a) Formation of symmetric and antisymmetric molecular orbitals from pairs of degenerate atomic orbitals. b) Analogous proposed formation of D-D states with different energies due to stronger or weaker conjugation across *meta*- or *para*- bridges in  $(o,m)ACA$  ( $pD-D$ ) and  $(o,o)ACA$  ( $mD-D$ ). c) Different D-D energies and extents of interaction with the acceptor-centred LE triplet state ( ${}^3LE_A$ ) lead to different experimental triplet energies. All orbital representations and implied relative state energies are indicative only.

The lower triplet energy in  $(o,m)ACA$  is therefore identified as an emergent property of the pair of donors. This lowering of triplet energy is irrelevant to the analogous *oDA* or *mDA* materials, and is impossible to predict by considering these fragments in isolation. These results therefore demonstrate that a ‘bottom-up’ approach to understanding TADF materials – recently espoused for 4CzIPN<sup>52</sup> – is simply untenable as it cannot account for these kinds of emergent higher-order effects. We also suggest that much of the complex photophysics of 4CzIPN is more likely attributable to the presence of persistent dimer species.<sup>34,50,51</sup>

Although based on well-established principles of molecular orbital theory, much of the previous explanation is speculative. Nonetheless some evidence for the existence of the proposed D-D states can be found in the experimental absorption spectra (Figure S9). In DPEPO films and a range of solvents we consistently observe a redshift in the main absorbance band (peak at  $\sim 275$  nm, attributed to DMAC) in  $(o,m)ACA$  compared to  $(o,o)ACA$ . We suggest that this redshift is due to the presence of a weak underlying band associated with excitation of the  $pD-D$  singlet state. In  $(o,o)ACA$  the  $mD-D$  state is expected to exist at higher energies, and therefore remains subsumed by the main donor DMAC absorption band. These D-D states then go on to influence the relevant LE triplet energy in each material. Furthermore, the absorbance spectra also show the same weak direct CT absorption bands in both  $(o,o)ACA$  and  $(o,m)ACA$  at  $\sim 375$  nm. In each material this band corresponds to two closely spaced (unresolved) CT state absorptions, consistent with the DFT calculations and prior understanding of the *oDA* or *mDA* materials. In both cases this indicates that formation of the CT



state involves only a single donor, and is unimpacted by the presence of the other (consistent with both materials sharing the same PL spectrum). View Article Online  
DOI: 10.1039/D1TC04171A

Because *(o,m)*ACA and *(o,o)*ACA introduce minimum additional complexity compared to *o*DA or *m*DA, there are few other explanations aside from D-D interactions that can potentially explain the trends seen here. While an intuitively satisfying example of basic physical chemistry principles in action, these results also demonstrate a new method of control in TADF materials. In contrast to external host-tuning of CT singlet states to minimise  $\Delta E_{ST}$ ,<sup>3</sup> multi-donor interactions may in future be used as a tool to selectively tune triplet states. These results also firmly demonstrate that ‘bottom-up’ approaches to understanding TADF materials are overly simplistic, and that understanding the properties of D-A-D materials purely in terms of their D-A subunits may not be a generally achievable goal.

## Conclusion

Two D-A-D TADF materials were compared with analogous D-A compounds. Despite displaying near-identical singlet energies and PLQYs, the triplet energies – and subsequent TADF performances – were markedly different and showed opposite trends as the D-A materials. We suggest that molecular orbital interactions with higher energy multi-donor LE states are responsible for these unexpected changes in triplet energy, with interaction strength modulated by the linkage patterns of the two donor subunits. The identification of these emergent multi-donor effects – not complicated here by any additional impacts of steric environment changes – demonstrates that bottom-up approaches to understanding TADF behaviour are unlikely to succeed. This includes the previously coveted ability of extrapolating D-A-D properties from those of smaller D-A fragments. These multi-donor effects nonetheless demonstrate a new approach for selectively tuning molecular triplet states, which may work in tandem with more well-established host-tuning of excited singlet states.

## Acknowledgements

The Authors thank Dr Dmitry S. Yufit of the Durham crystallography service for XRD measurements and technical support.

The Authors also thank the European Union’s Horizon 2020 Research and Innovation Programme for funding under Grant agreements No. 641725 (PHEBE), 674990 (EXCILIGHT), 732013 (HYPEROLED), and 812872 (TADFlife). ANB acknowledges an EPSRC Doctoral Training Grant.

## References

- 1 K. Wang, C.-J. Zheng, W. Liu, K. Liang, Y.-Z. Shi, S.-L. Tao, C.-S. Lee, X.-M. Ou and X.-H. Zhang, *Adv. Mater.*, 2017, **29**, 1701476.
- 2 J. Chen, T. Yu, E. Ubba, Z. Xie, Z. Yang, Y. Zhang, S. Liu, J. Xu, M. P. Aldred and Z. Chi, *Adv. Opt. Mater.*, 2019, **7**, 1801593.
- 3 P. L. Dos Santos, J. S. Ward, M. R. Bryce and A. P. Monkman, *J. Phys. Chem. Lett.*, 2016, **7**, 3341–3346.
- 4 T.-T. Bui, F. Goubard, M. Ibrahim-Ouali, D. Gigmes and F. Dumur, *Beilstein J. Org. Chem.*, 2018, **14**, 282–308.
- 5 F. Ni, N. Li, L. Zhan and C. Yang, *Adv. Opt. Mater.*, 2020, **8**, 1902187.
- 6 A. Steinegger, I. Klimant and S. M. Borisov, *Adv. Opt. Mater.*, 2017, **5**, 1700372.



- 7 F. B. Dias, K. N. Bourdakos, V. Jankus, K. C. Moss, K. T. Kamtekar, V. Bhalla, J. Santos, M. R. Bryce and A. P. Monkman, *Adv. Mater.*, 2013, **25**, 3707–3714. View Article Online  
DOI: 10.1039/D1TC04171A
- 8 Z. Yang, Z. Mao, C. Xu, X. Chen, J. Zhao, Z. Yang, Y. Zhang, W. Wu, S. Jiao, Y. Liu, M. P. Aldred and Z. Chi, *Chem. Sci.*, 2019, **10**, 8129–8134.
- 9 J. Gibson, A. P. Monkman and T. J. Penfold, *ChemPhysChem*, 2016, **17**, 2956–2961.
- 10 F. B. Dias, T. J. Penfold and A. P. Monkman, *Methods Appl. Fluoresc.*, 2017, **5**, 012001.
- 11 T. Cardeynals, S. Paredis, A. Danos, D. Vanderzande, A. P. Monkman, B. Champagne and W. Maes, *Dyes Pigm.*, 2021, **186**, 109022.
- 12 T. Cardeynals, S. Paredis, A. Danos, A. Harrison, J. Deckers, S. Brebels, L. Lutsen, D. Vanderzande, A. P. Monkman, B. Champagne et al. *Dyes Pigm.*, 2021, **190**, 109301.
- 13 P. Stachelek, J. S. Ward, P. L. Dos Santos, A. Danos, M. Colella, N. Haase, S. J. Raynes, A. S. Batsanov, M. R. Bryce and A. P. Monkman, *ACS Appl. Mater. Interfaces*, 2019, **11**, 27125–27133.
- 14 I. E. Serdiuk, C. H. Ryoo, K. Kozakiewicz, M. Mońka, B. Liberek and S. Y. Park, *J. Mater. Chem. C*, 2020, **8**, 6052–6062.
- 15 A. Shang, T. Lu, H. Liu, C. Du, F. Liu, D. Jiang, J. Min, H. Zhang and P. Lu, *J. Mater. Chem. C*, 2021, **9**, 7392–7399.
- 16 H. L. Lee, K. H. Lee, J. Y. Lee and H. J. Lee, *J. Mater. Chem. C*, 2021, **9**, 7328–7335.
- 17 Y. Im, M. Kim, Y. J. Cho, J.-A. Seo, K. S. Yook and J. Y. Lee, *Chem. Mater.*, 2017, **29**, 1946–1963.
- 18 Y. Pan, W. Li, S. Zhang, L. Yao, C. Gu, H. Xu, B. Yang and Y. Ma, *Adv. Opt. Mater.*, 2014, **2**, 510–515.
- 19 Y. H. Lee, S. Park, J. Oh, S.-J. Woo, A. Kumar, J.-J. Kim, J. Jung, S. Yoo and M. H. Lee, *Adv. Opt. Mater.*, 2018, 1800385.
- 20 D. De Sa Pereira, D. R. Lee, N. A. Kukhta, K. H. Lee, C. L. Kim, A. S. Batsanov, J. Y. Lee and A. P. Monkman, *J. Mater. Chem. C*, 2019, **7**, 10481–10490.
- 21 M. Colella, A. Danos and A. P. Monkman, *J. Phys. Chem. Lett.*, 2019, **10**, 793–798.
- 22 S. Kumar, L. G. Franca, K. Stavrou, E. Crovini, D. B. Cordes, A. M. Z. Slawin, A. P. Monkman and E. Zysman-Colman, *J. Phys. Chem. Lett.*, 2021, **12**, 2820–2830.
- 23 Y. Wada, H. Nakagawa, S. Matsumoto, Y. Wakisaka and H. Kaji, *Nat. Photonics*, 2020, **14**, 643–649.
- 24 Y. Kondo, K. Yoshiura, S. Kitera, H. Nishi, S. Oda, H. Gotoh, Y. Sasada, M. Yanai and T. Hatakeyama, *Nat. Photonics*, 2019, **13**, 678–682.
- 25 X. Tang, L. S. Cui, H. C. Li, A. J. Gillett, F. Auras, Y. K. Qu, C. Zhong, S. T. E. Jones, Z. Q. Jiang, R. H. Friend and L. S. Liao, *Nat. Mater.*, 2020, **19**, 1332–1338.
- 26 J. Wei, C. Zhang, D. Zhang, Y. Zhang, Z. Liu, Z. Li, G. Yu and L. Duan, *Angew. Chem. Int. Ed.*, 2021, **60**, 12269–12273.
- 27 Y. Wada, K. Shizu and H. Kaji, *J. Phys. Chem. A*, 2021, **125**, 4534–4539.
- 28 R. Huang, J. Avó, T. Northey, E. Channing-Pearce, P. L. dos Santos, J. S. Ward, P. Data, M. K. Etherington, M. A. Fox, T. J. Penfold et al. *J. Mater. Chem. C*, 2017, **5**, 6269–6280.
- 29 N. A. Kukhta, H. F. Higginbotham, T. Matulaitis, A. Danos, A. N. Bismillah, N. Haase, M. K.



- Etherington, D. S. Yufit, P. R. McGonigal, J. V. Gražulevičius et al. *J. Mater. Chem. C*, 2019, **7**, 9184–9194. Open Access Article Online  
DOI: 10.1039/D1TC04171A
- 30 T. Matulaitis, P. Imbrasas, N. A. Kukhta, P. Baronas, T. Bučiūnas, D. Banevičius, K. Kazlauskas, J. V. Gražulevičius and S. Juršėnas, *J. Phys. Chem. C*, 2017, **121**, 23618–23625.
  - 31 F. M. Xie, J. X. Zhou, Y. Q. Li and J. X. Tang, *J. Mater. Chem. C*, 2020, **8**, 9476–9494.
  - 32 T. Sudyoasuk, S. Petdee, C. Kaiyasuan, C. Chaiwai, P. Wongkaew, S. Namuangruk, P. Chasing and V. Promarak, *J. Mater. Chem. C*, 2021, **9**, 6251–6256.
  - 33 Y. Xu, C. Li, Z. Li, Q. Wang, X. Cai, J. Wei and Y. Wang, *Angew. Chem. Int. Ed.*, 2020, **59**, 17442–17446.
  - 34 L. Salah, M. K. Etherington, A. Shuaib, A. Danos, A. A. Nazeer, B. Ghazal, A. Prlj, A. T. Turley, A. Mallick, P. R. McGonigal et al. *J. Mater. Chem. C*, 2021, **9**, 189–198.
  - 35 L. S. Cui, H. Nomura, Y. Geng, J. U. Kim, H. Nakanotani and C. Adachi, *Angew. Chem. Int. Ed.*, 2017, **56**, 1571–1575.
  - 36 J. Lee, K. Shizu, H. Tanaka, H. Nomura, T. Yasuda and C. Adachi, *J. Mater. Chem. C*, 2013, **1**, 4599–4604.
  - 37 B. Huang, Q. Qi, W. Jiang, J. Tang, Y. Liu, W. Fan, Z. Yin, F. Shi, X. Ban, H. Xu and Y. Sun, *Dyes Pigm.*, 2014, **111**, 135–144.
  - 38 B. Li, Z. Li, F. Guo, J. Song, X. Jiang, Y. Wang, S. Gao, J. Wang, X. Pang, L. Zhao and Y. Zhang, *ACS Appl. Mater. Interfaces*, 2020, **12**, 14233–14243.
  - 39 K. Kawasumi, T. Wu, T. Zhu, H. S. Chae, T. Van Voorhis, M. A. Baldo and T. M. Swager, *J. Am. Chem. Soc.*, 2015, **137**, 11908–11911.
  - 40 K. Shizu, H. Tanaka, M. Uejima, T. Sato, K. Tanaka, H. Kaji and C. Adachi, *J. Phys. Chem. C*, 2015, **119**, 1291–1297.
  - 41 S. Xu, T. Liu, Y. Mu, Y.-F. Wang, Z. Chi, C.-C. Lo, S. Liu, Y. Zhang, A. Lien and J. Xu, *Angew. Chem. Int. Ed. Engl.*, 2015, **54**, 874–878.
  - 42 Y. Chen, J. Guo, X. Wu, D. Jia and F. Tong, *Dyes Pigm.*, 2018, **148**, 180–188.
  - 43 Z. Xie, C. Chen, S. Xu, J. Li, Y. Zhang, S. Liu, J. Xu and Z. Chi, *Angew. Chem. Int. Ed.*, 2015, **54**, 7181–7184.
  - 44 D. Gudeika, O. Bezikonny, D. Volyniuk and J. V. Gražulevičius, *Dyes Pigm.*, 2020, **172**, 107789.
  - 45 H. L. Lee, H. J. Jang and J. Y. Lee, *J. Mater. Chem. C*, 2020, **8**, 10302–10308.
  - 46 M. Aydemir, S. Xu, C. Chen, M. R. Bryce, Z. Chi and A. P. Monkman, *J. Phys. Chem. C*, 2017, **121**, 17764–17772.
  - 47 N. A. Kukhta and M. R. Bryce, *Mater. Horizons*, 2021, **8**, 33–55.
  - 48 G. Haykir, M. Aydemir, A. Danos, S. Gumus, G. Hizal, A. P. Monkman and F. Turksoy, *Dyes Pigm.*, 2021, **194**, 109579.
  - 49 H. Uoyama, K. Goushi, K. Shizu, H. Nomura and C. Adachi, *Nature*, 2012, **492**, 234–238.
  - 50 E. Cho, M. Hong, V. Coropceanu and J. L. Brédas, *Adv. Opt. Mater.*, 2021, 2002135.
  - 51 M. K. Etherington, N. A. Kukhta, H. F. Higginbotham, A. Danos, A. N. Bismillah, D. R. Graves, P. R. McGonigal, N. Haase, A. Morherr, A. S. Batsanov et al. *J. Phys. Chem. C*, 2019, **123**, 11109–11117.



- 52 H. Noda, X. K. Chen, H. Nakanotani, T. Hosokai, M. Miyajima, N. Notsuka, Y. Kashima, J. L. Brédas and C. Adachi, *Nat. Mater.*, 2019, **18**, 1084–1090. View Article Online  
DOI: 10.1039/D1TC04171A
- 53 D. Zhang, X. Song, A. J. Gillett, B. H. Drummond, S. T. E. Jones, G. Li, H. He, M. Cai, D. Credgington and L. Duan, *Adv. Mater.*, 2020, **32**, 1908355.
- 54 H. Noda, H. Nakanotani and C. Adachi, *Sci. Adv.*, 2018, **4**, eaao6910.
- 55 U. Balijapalli, M. Tanaka, M. Auffray, C. Y. Chan, Y. T. Lee, Y. Tsuchiya, H. Nakanotani and C. Adachi, *ACS Appl. Mater. Interfaces*, 2020, **12**, 9498–9506.
- 56 C. S. Oh, D. D. S. Pereira, S. H. Han, H. J. Park, H. F. Higginbotham, A. P. Monkman and J. Y. Lee, *ACS Appl. Mater. Interfaces*, 2018, **10**, 35420–35429.
- 57 N. R. Paisley, C. M. Tonge and Z. M. Hudson, *Front. Chem.*, 2020, **8**, 229.
- 58 C. S. Oh, H. L. Lee, S. H. Han and J. Y. Lee, *Chem. - A Eur. J.*, 2019, **25**, 642–648.
- 59 R. Ansari, W. Shao, S.-J. Yoon, J. Kim and J. Kieffer, *ACS Appl. Mater. Interfaces*, 2021, **13**, 28529–28537.
- 60 K. Stavrou, L. G. Franca and A. P. Monkman, *ACS Appl. Electron. Mater.*, 2020, **2**, 2868–2881.
- 61 R. Huang, N. A. Kukhta, J. S. Ward, A. Danos, A. S. Batsanov, M. R. Bryce and F. B. Dias, *J. Mater. Chem. C*, 2019, **7**, 13224–13234.
- 62 M. Colella, A. Danos and A. P. Monkman, *J. Phys. Chem. Lett.*, 2019, **10**, 793–798.
- 63 N. Haase, A. Danos, C. Pflumm, A. Morherr, P. Stachelek, A. Mekic, W. Brütting and A. P. Monkman, *J. Phys. Chem. C*, 2018, **122**, 29173–29179.
- 64 J. S. Ward, A. Danos, P. Stachelek, M. A. Fox, A. S. Batsanov, A. P. Monkman and M. R. Bryce, *Mater. Chem. Front.*, 2020, **4**, 3602–3615.
- 65 K. Stavrou, A. Danos, T. Hama, T. Hatakeyama and A. Monkman, *ACS Appl. Mater. Interfaces*, 2021, **13**, 8643–8655.
- 66 E. Aksoy, A. Danos, C. Varlikli and A. P. Monkman, *Dyes Pigm.*, 2020, **183**, 108707.
- 67 M. Colella, A. Danos and A. P. Monkman, *J. Phys. Chem. C*, 2019, **123**, 17318–17324.
- 68 H. Noda, R. Kabe and C. Adachi, *Chem. Lett.*, 2016, **45**, 1463–1466.
- 69 C. Y. Chan, M. Tanaka, Y. T. Lee, Y. W. Wong, H. Nakanotani, T. Hatakeyama and C. Adachi, *Nat. Photonics*, 2021, **15**, 203–207.
- 70 S. O. Jeon, K. H. Lee, J. S. Kim, S. G. Ihn, Y. S. Chung, J. W. Kim, H. Lee, S. Kim, H. Choi and J. Y. Lee, *Nat. Photonics*, 2021, **15**, 208–215.
- 71 S. H. Han, J. H. Jeong, J. W. Yoo and J. Y. Lee, *J. Mater. Chem. C*, 2019, **7**, 3082–3089.
- 72 N. Haase, A. Danos, C. Pflumm, P. Stachelek, W. Brütting and A. P. Monkman, *Mater. Horizons*, 2021, **8**, 1805.
- 73 T. B. Nguyen, H. Nakanotani, T. Hatakeyama and C. Adachi, *Adv. Mater.*, 2020, **32**, 1906614.
- 74 Gaussian 09, Revision A.02, M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, G. A. Petersson, H. Nakatsuji, X. Li, M. Caricato, A. Marenich, J. Bloino, B. G. Janesko, R. Gomperts, B. Mennucci, H. P. Hratchian, J. V. Ortiz, A. F. Izmaylov, J. L. Sonnenberg, D. Williams-Young, F. Ding, F. Lipparini, F. Egidi, J. Goings, B. Peng, A. Petrone, T. Henderson, D. Ranasinghe, V. G. Zakrzewski, J. Gao, N. Rega, G. Zheng, W. Liang, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa,





- M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, K. Throssell, J. A. Montgomery, Jr., J. E. Peralta, F. Ogliaro, M. Bearpark, J. J. Heyd, E. Brothers, K. N. Kudin, V. N. Staroverov, T. Keith, R. Kobayashi, J. Normand, K. Raghavachari, A. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, J. M. Millam, M. Klene, C. Adamo, R. Cammi, J. W. Ochterski, R. L. Martin, K. Morokuma, O. Farkas, J. B. Foresman, and D. J. Fox, Gaussian, Inc., Wallingford CT, 2016.
- 75 K. S. Thanthiriwatte and S. R. Gwaltney, *J. Phys. Chem. A*, 2006, **110**, 2434–2439.
- 76 N. A. Kukhta, D. A. da Silva Filho, D. Volyniuk, J. V. Grazulevicius and G. Sini, *Chem. Mater.*, 2017, **29**, 1695–1707.
- 77 N. A. Kukhta, A. S. Batsanov, M. R. Bryce and A. P. Monkman, *J. Phys. Chem. C*, 2018, **122**, 28564–28575.
- 78 N. A. Kukhta, R. Huang, A. S. Batsanov, M. R. Bryce and F. B. Dias, *J. Phys. Chem. C*, 2019, **123**, 26536–26546.
- 79 Fan, J.; Zhang, Y.; Zhou, Y.; Lin, L.; Wang, C.-K. *J. Phys. Chem. C* 2018, **122**, 2358–2366
- 80 S. Feng, K. Wen, Y. Si, X. Guo and J. Zhang, *J. Comput. Chem.*, 2018, **39**, 2601–2606
- 81 A. D. Boese and J. M. L. Martin, *J. Chem. Phys.*, 2004, **121**, 3405–3416.
- 82 D. De Sa Pereira, C. Menelaou, A. Danos, C. Marian and A. P. Monkman, *J. Phys. Chem. Lett.*, 2019, **10**, 3205–3211.
- 83 M. K. Etherington, J. Gibson, H. F. Higginbotham, T. J. Penfold and A. P. Monkman, *Nat. Commun.*, 2016, **7**, 1–7.
- 84 M. Hempe, N. A. Kukhta, A. Danos, M. A. Fox, A. S. Batsanov, A. P. Monkman and M. R. Bryce, *Chem. Mater.*, 2021, **33**, 3066–3080.
- 85 S. A. Bagnich, S. Athanasopoulos, A. Rudnick, P. Schroegel, I. Bauer, N. C. Greenham, P. Strohriegel and A. Köhler, *J. Phys. Chem. C*, 2015, **119**, 2380–2387.
- 86 I. A. Wright, A. Danos, S. Montanaro, A. S. Batsanov, A. P. Monkman and M. R. Bryce, *Chem. - A Eur. J.*, 2021, **27**, 6545–6556.

View Article Online

DOI: 10.1039/D1TC04171A

